

Production of a hydraulic material from post treated steelmaking slags

K. Schraut^{1*}, B. Adamczyk², C. Adam³, D. Stephan⁴, S. Simon⁵, J. von Werder⁶, and B. Meng⁷

¹ Bundesanstalt für Materialforschung und -prüfung (BAM), Berlin, Germany
Email: katharina.schraut@bam.de

² Bundesanstalt für Materialforschung und -prüfung (BAM), Berlin, Germany
Email: burkart.adamczyk@bam.de

³ Bundesanstalt für Materialforschung und -prüfung (BAM), Berlin, Germany
Email: christian.adam@bam.de

⁴ Technische Universität Berlin, Berlin, Germany
Email: stephan@tu-berlin.de

⁵ Bundesanstalt für Materialforschung und -prüfung (BAM), Berlin, Germany
Email: sebastian.simon82@gmail.com

⁶ Bundesanstalt für Materialforschung und -prüfung (BAM), Berlin, Germany
Email: Julia.von-Werder@bam.de

⁷ Bundesanstalt für Materialforschung und -prüfung (BAM), Berlin, Germany
Email: Birgit.Meng@bam.de

ABSTRACT

Steelmaking slag is a by-product of steel production, of which 4.5 Mt were produced in 2020 in Germany alone. It is mainly used in road construction, earthwork and hydraulic engineering. A smaller part is returned to the metallurgical cycle, used as fertiliser or landfilled.

With this use, iron oxides still contained in steelmaking slag are lost. In addition, the possibility of producing higher-grade products from steelmaking slag is foregone. In recent decades, many researchers have investigated the production of Portland cement clinker and crude iron from basic oxygen furnace slags (BOFS) via a reductive treatment. Carbothermal treatment of liquid BOFS causes a reduction of iron oxides to metallic iron, which separates from the mineral phase due to its higher density. Simultaneously, the chemical composition of the reduced slag is adapted to that of Portland cement clinker.

In this study, German BOFS was reduced in a small-scale electric arc furnace using petrol coke as a reducing agent. The resulting low-iron mineral product has a similar chemical composition to Portland cement clinker and was rich in the tricalcium silicate solid solution alite (Ca₃SiO₅). Based on its chemical and mineralogical composition, similar to that of Portland cement clinker, the reduced BOFS has the potential to react comparably. In our study, the reduced BOFS produced less hydration heat than OPC, and its hydraulic reaction was delayed. However, adding gypsum has shown to accelerate the hydration rate of the reduced BOFS compared to that known from the calcium silicates of Portland cement clinker. Further research to improve the hydraulic properties of the reduced slag is essential. If successful, producing a hydraulic binder and crude iron from BOFS has economic and ecological benefits for both the cement and steel industries.

KEYWORDS: *steelmaking slag, alite, hydraulic reactivity, clinker substitute*

1. Introduction

Basic oxygen furnace slags (BOFS) contain 7–50 wt.% Fe₂O₃, 31–56 wt.% CaO, 10–27 wt.% SiO₂, 1–4.5 wt.% Al₂O₃, 0.3–10 wt.% Mn₂O₃, and 0.8–15 wt.% MgO (Menad et al., 2014). Despite their high basicity (CaO/SiO₂ ratio) and a content of up to 20 wt.% alite (Ca₃SiO₅) and up to 60 wt.% belite (β-Ca₂SiO₄) (Das et al., 2007), BOFS are scarcely used for cement production due to their high iron oxides content, low content of hydraulic phases, and content of up to 15 wt.% free CaO and 5 wt.% MgO, which make BOFS a risk for volume instability (Das et al., 2007, Waligora et al., 2010, Menad et al., 2014).

In the past, several different ways to produce a hydraulic or pozzolanic material from BOFS have been investigated, e.g. (Li et al., 2011, Belhadj et al., 2012, Ludwig and Wulfert, 2012, Li et al., 2013, Neto et al., 2017, Liu et al., 2019). A reductive treatment of BOFS as described in (Kubodera et al., 1979, Piret and Dralants, 1984, Dziarmagowski et al., 1992, Reddy et al., 2006, Ludwig and Wulfert, 2012, Wulfert et al., 2013a, Wulfert et al., 2013b, Liu et al., 2017) is advantageous because it allows both the recovery of iron from the BOFS and the simultaneous production of Portland cement clinker. The properties of the final hydraulic product depend on the composition of the original BOFS, the degree of reduction, and the modifications made during the treatment.

However, it was found that the hydraulic reaction of the Portland cement clinker-like material produced from BOFS was significantly delayed compared to ordinary Portland cement (OPC) (Schraut et al., 2021). Since OPC is a product of finely ground cement clinker mixed with a certain amount of calcium sulfates, such as gypsum ($\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$), the next step was to investigate the hydraulic reactivity of the clinker-like material from BOFS with the addition of gypsum. Besides controlling the tricalcium aluminate reaction, calcium sulfates also accelerate the hydration of calcium silicates (Bentur, 1976, Quennoz and Scrivener, 2013) and increase the dissolution of alite (Menetrier et al., 1980).

To keep the complexity of the system low, the addition of calcium sulfates other than gypsum has been refrained from in this study.

2. Materials and Methods

A BOFS from a German steel plant was used for the thermochemical experiments. The slag was crushed to a maximum grain size of approx. 20 mm and dried at 200 °C before it was molten and reduced in the small technical scale electric arc furnace of the Bundesanstalt für Materialforschung und -prüfung (BAM). The electric arc furnace has a power of 480 kW and is equipped with three graphite electrodes with a diameter of 60 mm. The experiments were conducted in a graphite-lined furnace vessel with a volume of approx. 0.4 m³. 58 g of petrol coke per kg of BOFS was added as a reducing agent. The generated metallic iron was sedimented at the bottom of the furnace and was obtained manually after cooling. Cooling took place in the reactor within ~24 h. For more details, see Schraut et al. (2021).

The chemical composition of the samples was determined by CRB Analyse Service GmbH on fused beads by X-ray fluorescence analysis (XRF). The crystalline phase composition was determined by X-ray diffraction (XRD) with a Bruker D8 Advance X-ray diffraction system at 40 kV and 40 mA over an angular range of 5–85 °2θ with a step size of 0.02 °2θ and a velocity of 2 s/step. The instrument was equipped with a Cu-tube, a LynxEye XE-T detector, and a fixed slit (0.3°). To investigate the crystalline hydrates with XRD, the hydration was stopped after 2, 7, 14, 28, 56, and 90 d using the solvent exchange method with isopropanol.

The hydration heat was measured over two weeks in an isothermal calorimeter TAM Air 8-channel from TA instruments at a temperature of 20 °C. 3 g of the ground sample was externally mixed for 1 min with 1.5 g distilled water resulting in a water-to-binder (W/B)-ratio of 0.5.

As a reference, a commercial CEM I 32.5 R from Schwenk Zement KG was prepared and analysed under the same conditions as the experimental samples. Gypsum (EMSURE® p.A. from Merck KGaA) was added to the sample in a concentration corresponding to 1.0 wt.% SO₃.

3. Results and Discussion

The reductive treatment resulted in a transformation of the oxide-bound iron in brownmillerite ($\text{Ca}_2(\text{Al,Fe})_2\text{O}_5$), wuestite (FeO) and magnetite (Fe_3O_4) to metallic iron, which separated from the mineral slag. Accordingly, the mass fraction of Fe₂O₃ in the mineral slag (reduced BOFS) decreased from about 29 wt.% to about 6 wt.%, while the mass fractions of CaO and SiO₂ increased proportionally (Table 1). The mineralogical composition of the reduced BOFS changed correspondingly. While the Fe-oxides and Fe-Al-oxides disappeared, alite formed the new main mineral phase in the reduced BOFS. Besides alite, belite, mayenite ($\text{Ca}_{12}\text{Al}_{14}\text{O}_{33}$), tricalcium aluminate ($\text{Ca}_3\text{Al}_2\text{O}_6$), portlandite ($\text{Ca}(\text{OH})_2$) and periclase (MgO) were identified in the reduced BOFS as crystalline phases. Therefore, it can be stated that the mineralogical and chemical composition of the reduced BOFS is close to the mineralogical and chemical composition of Portland cement clinker.

The formation of alite in reduced BOFS was also reported by Kubodera et al. (1979), Wulfert et al. (2013b) and Dziarmagowski et al. (1992) and is likely to depend on the CaO/SiO₂-ratio of the reduced slag. Alite was identified as the main mineral in reduced BOFS with CaO/SiO₂ > 2.9, while belite was the main mineral in reduced BOFS with CaO/SiO₂ < 2.6 (Dziarmagowski et al., 1992, Reddy et al., 2006).

Table 1: Chemical composition of the original BOFS, the reduced BOFS (rBOFS), and a commercial OPC CEM I 32.5 R (CEM I) determined by XRF. All mass fractions are given as wt.% oxides, although this may not always represent the actual oxidation state of each element in the samples. Only element oxides whose mass fractions were > 0.1 wt.% in at least one sample are shown.

[wt.%]	CaO	SiO ₂	Fe ₂ O ₃	MnO	MgO	Al ₂ O ₃	P ₂ O ₅	Cr ₂ O ₃	TiO ₂	V ₂ O ₅	SO ₃	SrO	Na ₂ O	K ₂ O
BOFS	43.48	12.07	28.59	4.554	3.64	1.79	1.12	0.518	0.524	0.310	0.23	0.025	0.07	<0.03
rBOFS	64.00	19.54	5.64	3.151	3.15	2.53	1.20	0.419	0.730	0.399	0.05	0.035	<0.06	<0.03
CEM I	61.97	19.36	3.06	0.047	3.04	4.96	0.44	0.013	0.322	0.010	3.03	0.148	0.21	0.92

The main hydration reaction of the reduced BOFS was considerably slower than that of OPC and started only after ~9 d of hydration (Figure 1). The hydration heat maximum was reached after about 14 d of hydration. The cumulative heat of hydration after 14.5 d was ~90 J/g. The first hydrates to form were portlandite (Ca(OH)₂) and brucite (Mg(OH)₂). Additionally, hemicarboaluminate ([Ca₄Al₂(OH)₁₂][OH(CO₃)_{0.5}·4H₂O]) was detected and transformed later to carbonated hemicarboaluminate ([Ca₄Al₂(OH)₁₂][OH_{0.4}(CO₃)_{0.8}·4H₂O]) and monocarboaluminate (Ca₄Al₂(OH)₁₂(CO₃)·5H₂O). The addition of 1 wt.% SO₃ in the form of gypsum accelerated the reaction of the reduced BOFS significantly. The main hydration reaction started after ~1 d of hydration and the cumulative heat of hydration after 14.5 d increased to ~160 J/g. Furthermore, the heat flow curve showed a sharp peak after ~2 d and 5 h that can be interpreted as the reaction peak of the aluminate reaction. Since the aluminate reaction occurred after the silicate reaction, the sample can be considered properly sulfated (Quennoz and Scrivener, 2013). In rBOFS + 1 wt.% SO₃, ettringite formed besides portlandite and brucite. No carboaluminates formed during hydration of rBOFS + 1 wt.% SO₃.

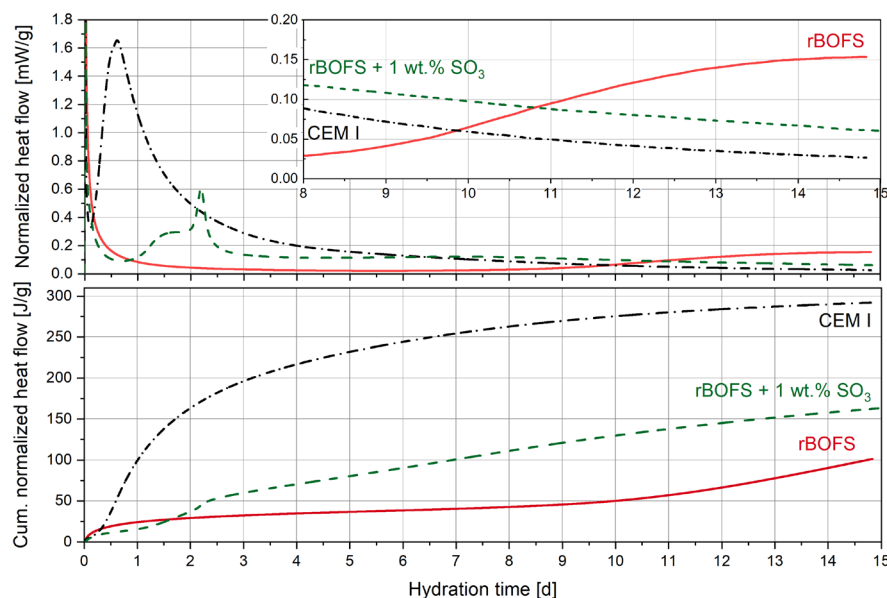


Figure 1: Normalised heat flow and cumulative normalised heat of the reduced BOFS (red, solid line), the reduced BOFS with the addition of an equivalent of 1 wt.% SO₃ as gypsum (green, dashed line) and of a commercial CEM I (black, dash-dotted line) measured for 14.5 d.

Sulfate is known to influence the silicate reaction. An accelerated dissolution of the alite with addition of sulfates was reported by (Bentur, 1976, Menetrier et al., 1980, Zajac et al., 2014, Bergold et al., 2017, Zunino and Scrivener, 2020, Andrade Neto et al., 2022). The reasons for this are still debated. The effect

was proposed to be caused by a promotion of C-S-H growth by ettringite acting as additional nuclei (Bergold et al., 2017, Tan et al., 2019) or by a change in C-S-H morphology (Andrade Neto et al., 2022). Other researchers assumed that a decrease of Ca^{2+} activity due to the formation of CaSO_4^0 species or an increased protonation of the C_3S surface by sulfate ions enhances the alite dissolution (Nicoleau et al., 2014). The binding of Al ions as ettringite is most likely not the causative agent, as acceleration by gypsum was observed in C_3S with and without Al (Andrade Neto et al., 2022).

4. Conclusions

The reductive treatment of BOFS can be used to recover iron from BOFS while simultaneously producing a material similar to Portland cement clinker. The majority of iron was reduced to metallic iron and separated from the mineral melt. The reduced BOFS had a chemical and mineralogical composition close to that of Portland cement clinker and contained alite as the main mineral.

The reduced BOFS reacted considerably more slowly with water than OPC. However, the reaction rate was increased with the addition of gypsum. Further investigations are needed, including using different sulfate carriers and SO_3 contents, to determine the actual mechanisms behind this acceleration. Nevertheless, the reduced BOFS shows potential as a cement component or concrete addition contributing to long-term hardening.

Acknowledgements

We would like to thank I. Feldmann for SEM pictures, D. Al-Sabbagh for XRD measurements and T. Hirsch for calorimetric measurements.

This work was funded by the German ministry of Education and Research (BMBF) under the funding guideline „Resource-efficient circular economy - Building and mineral cycles (ReMin)“ funding number 033R254A.

References

- Menad, N., Kanari, N. and Save, M. (2014) "Recovery of high grade iron compounds from LD slag by enhanced magnetic separation techniques", *International journal of mineral processing*, 126: 1-9
- Das, B., Prakash, S., Reddy, P. and Misra, V. (2007) "An overview of utilization of slag and sludge from steel industries", *Resources, Conservation and Recycling*, 50(1): 40-57
- Waligora, J., Bulteel, D., Degruilliers, P., Damidot, D., Potdevin, J. and Measson, M. (2010) "Chemical and mineralogical characterizations of LD converter steel slags: A multi-analytical techniques approach", *Materials characterization*, 61(1): 39-48
- Li, J., Yu, Q., Wei, J. and Zhang, T. (2011) "Structural characteristics and hydration kinetics of modified steel slag", *Cement and Concrete Research*, 41(3): 324-329
- Belhadj, E., Diliberto, C. and Lecomte, A. (2012) "Characterization and activation of basic oxygen furnace slag", *Cement and concrete composites*, 34(1): 34-40
- Ludwig, H. and Wulfert, H. (2012) 18. *Int. Baustofftagung ibausil*, pp. 18-25. Weimar
- Li, Z., Zhao, S., Zhao, X. and He, T. (2013) "Cementitious property modification of basic oxygen furnace steel slag", *Construction and Building Materials*, 48: 575-579
- Neto, J.B.F., Fredericci, C., Faria, J.O., Chotoli, F.F., Ribeiro, T.R., Malynowskyj, A., Silva, A.L., Quarcioni, V.A. and Lotto, A.A. (2017) "Modification of Basic Oxygen Furnace Slag for Cement Manufacturing", *Journal of Sustainable Metallurgy*, 3(4): 720-728
- Liu, C., Huang, S., Blanpain, B. and Guo, M. (2019) "Effect of Al_2O_3 Addition on Mineralogical Modification and Crystallization Kinetics of a High Basicity BOF Steel Slag", *Metallurgical and Materials Transactions B*, 50(1): 271-281
- Kubodera, S., Koyama, T., Ando, B. and Kondo, R. (1979) "An approach to the full utilization of LD slag", *Transactions of the Iron and Steel Institute of Japan*, 19(7): 419-427
- Piret, J. and Dralants, A. (1984) "Utilization of LD Process Slag for the Production of Portland Cement Clinker and Pig Iron", *Stahl und Eisen*, 104(16): 774-778
- Dziarmagowski, M., Karbowniczek, M., Pyzalski, M. and Okon, J. (1992) "Reduction of converter slag in electric arc furnace", *Ironmaking & steelmaking*, 19(1): 45-49
- Reddy, A.S., Pradhan, R. and Chandra, S. (2006) "Utilization of basic oxygen furnace (BOF) slag in the production of a hydraulic cement binder", *International journal of mineral processing*, 79(2): 98-105

- Wulfert, H., Keyssner, M., Ludwig, H. and Adamczyk, B. (2013a) "Metal recovery and conversion of steel slag into highly reactive cement components/Metallgewinnung und Umwandlung von LD-Schlacke in hochreaktive Zementkomponenten", *ZKG international*, 9: 34-40
- Wulfert, H., Keyßner, M., Ludwig, H., Adamczyk, B. and Schiffers, A. (2013b) "Hochreaktive Zementkomponenten aus Stahlwerksschlacken verbessern Ökologie und Ökonomie/ Highly reactive cement components from steel slag for optimized ecology and economy", *Stahl und Eisen*, 133(12): 45-50
- Liu, C., Huang, S., Wollants, P., Blanpain, B. and Guo, M. (2017) "Valorization of BOF steel slag by reduction and phase modification: metal recovery and slag valorization", *Metallurgical and Materials Transactions B*, 48(3): 1602-1612
- Schraut, K., Adamczyk, B., Adam, C., Stephan, D., Meng, B., Simon, S. and von Werder, J. (2021) "Synthesis and characterisation of alites from reduced basic oxygen furnace slags", *Cement and Concrete Research*, 147: 106518
- Bentur, A. (1976) "Effect of Gypsum on the Hydration and Strength of C₃S Pastes", *Journal of the American Ceramic Society*, 59(5- 6): 210-213
- Quennoz, A. and Scrivener, K.L. (2013) "Interactions between alite and C₃A-gypsum hydrations in model cements", *Cement and Concrete Research*, 44: 46-54
- Menetrier, D., Jawed, I. and Skalny, J. (1980) "Effect of gypsum on C₃S hydration", *Cement and Concrete Research*, 10(5): 697-701
- Zajac, M., Rossberg, A., Le Saout, G. and Lothenbach, B. (2014) "Influence of limestone and anhydrite on the hydration of Portland cements", *Cement and concrete composites*, 46: 99-108
- Bergold, S., Goetz-Neunhoeffler, F. and Neubauer, J. (2017) "Interaction of silicate and aluminate reaction in a synthetic cement system: Implications for the process of alite hydration", *Cement and Concrete Research*, 93: 32-44
- Zunino, F.A. and Scrivener, K. (2020) "Factors influencing the sulfate balance in pure phase C₃S/C₃A systems", *Cement and Concrete Research*, 133: 106085
- Andrade Neto, J.S., Rodríguez, E.D., Monteiro, P.J., De la Torre, A.G. and Kirchheim, A.P. (2022) "Hydration of C₃S and Al-doped C₃S in the presence of gypsum", *Cement and Concrete Research*, 152: 106686
- Tan, H., Li, M., Ren, J., Deng, X., Zhang, X., Nie, K., Zhang, J. and Yu, Z. (2019) "Effect of aluminum sulfate on the hydration of tricalcium silicate", *Construction and Building Materials*, 205: 414-424
- Nicoleau, L., Schreiner, E. and Nonat, A. (2014) "Ion-specific effects influencing the dissolution of tricalcium silicate", *Cement and Concrete Research*, 59: 118-138